

EKSMAL 1

Ready-mix self-leveling grout, with compensated shrinkage, used for grouting sections with thickness from 5 to 20 mm.

In compliance with EN 1504 – 3 Class R4 and EN 1504-6

FIELD OF APPLICATION

Eksmal 1 is used in structural reparation of concrete and reinforce-concrete elements, anchor grouting, grouting of foundations under heavy loaded structural elements, crane beams, base under machines etc.

PROPERTIES

- one-component powdery material;
- easy to prepare and apply;
- self – leveling;
- high early and final strength;
- compensate shrinkage caused by cement setting;
- excellent adhesion to concrete substrate;
- excellent durability performances;
- high elasticity module;
- resistant to atmospheric influences;

TECHNICAL FEATURES

Property	Method	Measured values	Declared values
Appearance	-	Grey powder	Grey powder
Water/material ratio	-	0,135	0.135 - 0.145
Maximal size of aggregate	-		1 mm
Specific density	EN 12190	2325 kg/m ³	(2320 - 2420) kg/m ³
Flow value			
after 5 min		≥40 cm	≥35 cm
after 15 min	EN 13395-2	≥45 cm	≥35 cm
after 30 min		≥45 cm	≥35 cm
after 60 min		≥40 cm	≥35 cm
Setting time			
Start of setting	EN 13294	02:57	(2÷4)h
End of setting		04:06	(3÷5)h
Compressive strength			
after 1 day	EN 12190	36.7 MPa	≥30 MPa
after 28 days		74.3 MPa	≥55 MPa
Adhesive bond	EN 1542	3.23 MPa	≥ 2,0 MPa
Restrained shrinkage/expansion	EN 12617-4	3.34/3.79 MPa	≥ 2,0 MPa
Thermal compatibility:	EN 13687-1		
Freeze-thaw cycling with de-icing salt immersion		3.94 MPa	≥2,0 MPa
Carbonization resistance		pass	dk≤ control
Capillary absorption	EN 13057	0,0671kg · m ⁻² · h ^{-0.5}	≤ 0,5 kg · m ⁻² · h ^{-0.5}

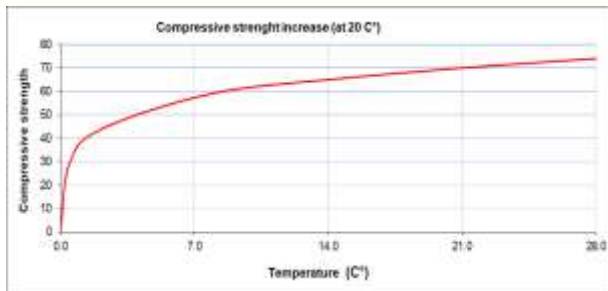


Diagram 1

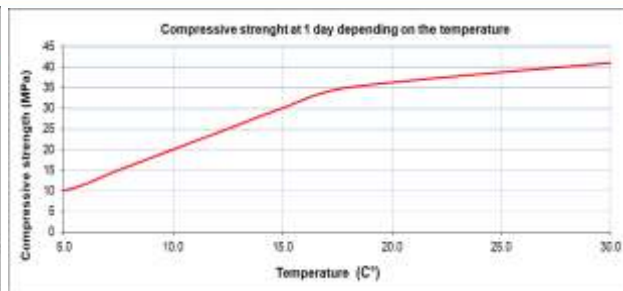


Diagram 2

METHOD STATEMENT

SUBSTRATE PREPARATION

Substrate on which Eksmal 1 is applied must be clean, all unstable sections must be removed, dust and oil free, and saturated with water. Surface temperature on which material is applied must be between 5°C and 30°C.

In case of reparation of damaged reinforced concrete structures, exposed reinforcement and anchors must be mechanically cleaned from corrosion, paint residues and oil (using a steel brush or sand-blasting).

APPLICATION

Eksmal 1 is mixed with required quantity of water- for one bag of material (25 kg) required quantity of water is 3.3 to 3.6 kg. Mixing is carried out with slow mixer (~500 rot/min) at least 3 minutes, until complete homogenization. Mixture is leaved to rest for 2-3 minutes, than mixed again and applied by grouting. Material must be protected from high temperatures (above 30°C), from exposure to direct sunlight and wind, as well as cured with water (or other appropriate curing method) in first few hours after application. It is recommended to use Eksmal 1 for grouting of sections with thickness up to 2 cm. For larger sections, it is recommended to use Eksmal with larger aggregate fractions (Eksmal 4,8,16,32). Reason for these recommendation is to improve economic aspect of the construction, as well as to reduce negative effects from exothermic processes that occur when concreting large concrete sections. For grouting large sections with small thickness, depending on the type of construction surface need to be divided in sections with construction joints, immediately after the setting of the material. In addition, joint can be filled with epoxy-based sealant (for obtaining flat monolith surface) or with elastic sealant (in cases when surface need to "work" – expand and contract during exploitation).

GROUTING OF ANCHORS

In cases when steel anchor is grouted with Eksmal 1, drilled hole (in which anchor is inserted) must be with diameter minimum 6 mm wider than anchor diameter (radius of the hole need to be minimum 3 mm wider than the anchor radius). Opening in which anchor is installed need to be clean, free of dust, and the surrounding concrete need to be saturated with water. In cases when anchor is installed horizontally on vertical surface hole need to be drilled with angle (slope pointing downward) in order to avoid spillage of the material. Eksmal 1 is poured in the anchor-hole (app. ½ of the depth) than anchor is inserted so the excess material will overflow, thus completely filling the space between anchor and the surrounding concrete.

CONSUMPTION

2000 to 2200 kg material are used for preparation of 1m³ Eksmal 1.

CLEANING

Tools and equipment are cleaned with water immediately after their use.

PACKAGING

Bags: 6 kg
Bags: 25 kg

STORAGE

In the original closed packaging, in dry free spaces at temperature between 5°C and 35°C. Shelf life: 12 months.

CE MARKING

<p style="text-align: center;">CE 2032</p>	
<p style="text-align: center;">ADING AD Skopje, Novoselski pat (ul 1409) br.11 1060 Skopje, North Macedonia 17, 20 GBCA001/6 EN 1504-3:2005 EN 1504-6:2006 EKSMAL 1 Concrete repair product for structural repair – mortar based on based on hydraulic cement (CC)</p>	
According to EN 1504-3	
Compressive strength	≥ 45 N/mm² (class R4)
Chloride ion content	≤ 0,05%
Adhesive bond	≥ 2,0 N/mm²
Restrained shrinkage/expansion	Bond strength after test ≥ 2,0 N/mm²
Carbonation resistance	d_k ≤ control concrete (MC 0,45)
Elastic modulus	≥ 20 GPa
Thermal compatibility: Freeze-thaw cycling with de-icing salt immersion	Bond strength after 50 cycles ≥ 2,0 N/mm²
Capillary absorption	≤ 0,5 kg/m² · h^{0,5}
Reaction to fire	Class A1
Dangerous substances	No performance determined
According to EN 1504-6	
Pull-out strength	Displacement ≤ 0,6 mm at load of 75kN

Health hazards: Eksmal 1 does not contain toxic materials. Nevertheless, avoid contact of the product with skin and eyes and avoid swallowing. In case of contact with skin or eyes, rinse it immediately with clean running water. If swallowed, seek medical assistance. Additional information are provided in the Safety Data Sheet of the product.

Fire: Eksmal 1 is non-flammable.

Cleaning and disposal: Loose residues of Eksmal 1 should be cleaned with water. Old and used packaging should be disposed of in accordance with local rules and regulations for that type of waste. Additional information are provided in the Safety Data Sheet of the product.